

Neodymium magnet

From Wikipedia, the free encyclopedia


A **neodymium magnet** (also known as **NdFeB**, **NIB** or **Neo** magnet), the most widely used^[1] type of rare-earth magnet, is a permanent magnet made from an alloy of neodymium, iron and boron to form the $\text{Nd}_2\text{Fe}_{14}\text{B}$ tetragonal crystalline structure.^[2] Developed in 1982 by General Motors and Sumitomo Special Metals, neodymium magnets are the strongest type of permanent magnet commercially available.^{[2][3]} They have replaced other types of magnets in the many applications in modern products that require strong permanent magnets, such as motors in cordless tools, hard disk drives and magnetic fasteners.



Nickel plated neodymium magnet on a bracket from a hard disk drive



Nickel-plated neodymium magnet cubes

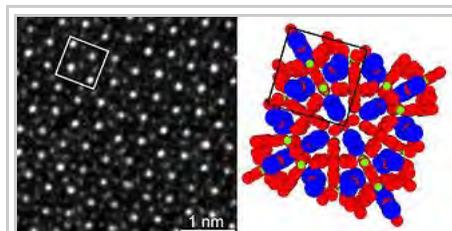

Left: High-resolution transmission electron microscopy image of $\text{Nd}_2\text{Fe}_{14}\text{B}$; right: crystal structure with unit cell marked

Contents

- 1 Description
- 2 History
- 3 Production
- 4 Properties
 - 4.1 Grades
 - 4.2 Magnetic properties
 - 4.3 Physical and mechanical properties
- 5 Corrosion problems
- 6 Hazards
- 7 Applications
 - 7.1 Existing magnet applications
 - 7.2 New applications
- 8 See also
- 9 References
- 10 Further reading
- 11 External links

Description

Neodymium is a metal which is ferromagnetic (more specifically it shows antiferromagnetic properties), meaning that like iron it can be magnetized to become a magnet, but its Curie temperature (the temperature above which its ferromagnetism disappears) is 19 K (−254 °C), so in pure form its magnetism only appears at extremely low temperatures.^[4] However, compounds of neodymium with transition metals such as iron can have Curie temperatures well above room temperature, and these are used to make neodymium magnets.

The strength of neodymium magnets is due to several factors. The tetragonal $\text{Nd}_2\text{Fe}_{14}\text{B}$ crystal structure has

exceptionally high uniaxial magnetocrystalline anisotropy ($H_A \sim 7$ teslas – magnetic field strength H in A/m versus magnetic moment in $A \cdot m^2$).^[5] This means a crystal of the material preferentially magnetizes along a specific crystal axis but is very difficult to magnetize in other directions. Like other magnets, the neodymium magnet alloy is composed of microcrystalline grains which are aligned in a powerful magnetic field during manufacture so their magnetic axes all point in the same direction. The resistance of the crystal lattice to turning its direction of magnetization gives the compound a very high coercivity (resistance to being demagnetized).

The neodymium atom also can have a large magnetic dipole moment because it has 7 unpaired electrons in its electron structure^[6] as opposed to about 3 in iron. In a magnet it is the unpaired electrons, aligned so they spin in the same direction, which generate the magnetic field. This gives the $Nd_2Fe_{14}B$ compound a high saturation magnetization ($J_s \sim 1.6$ T or 16 kG) and typically 1.3 teslas. Therefore, as the maximum energy density is proportional to J_s^2 , this magnetic phase has the potential for storing large amounts of magnetic energy ($BH_{max} \sim 512$ kJ/m³ or 64 MG·Oe). This magnetic energy value is about 18 times greater than "ordinary" magnets by volume. This property is higher in NdFeB alloys than in samarium cobalt (SmCo) magnets, which were the first type of rare-earth magnet to be commercialized. In practice, the magnetic properties of neodymium magnets depend on the alloy composition, microstructure, and manufacturing technique employed.

History

In 1982, General Motors (GM) and Sumitomo Special Metals discovered the $Nd_2Fe_{14}B$ compound. The research was initially driven by the high raw materials cost of SmCo permanent magnets, which had been developed earlier. GM focused on the development of melt-spun nanocrystalline $Nd_2Fe_{14}B$ magnets, while Sumitomo developed full-density sintered $Nd_2Fe_{14}B$ magnets.

GM commercialized its inventions of isotropic Neo powder, bonded Neo magnets, and the related production processes by founding Magnequench in 1986 (Magnequench has since become part of Neo Materials Technology, Inc., which later merged into Molycorp). The company supplied melt-spun $Nd_2Fe_{14}B$ powder to bonded magnet manufacturers.

The Sumitomo facility became part of the Hitachi Corporation, and currently manufactures and licenses other companies to produce sintered $Nd_2Fe_{14}B$ magnets. Hitachi holds more than 600 patents covering neodymium magnets.^[7]

Chinese manufacturers have become a dominant force in neodymium magnet production, based on their control of much of the world's sources of rare earth mines.^[8]

The United States Department of Energy has identified a need to find substitutes for rare earth metals in permanent magnet technology, and has begun funding such research. The Advanced Research Projects Agency-Energy has sponsored a Rare Earth Alternatives in Critical Technologies (REACT) program, to develop alternative materials. In 2011, ARPA-E awarded 31.6 million dollars to fund Rare-Earth Substitute projects.^[9]

Production

There are two principal neodymium magnet manufacturing methods:

- Classical powder metallurgy or sintered magnet process^[10]
- Rapid solidification or bonded magnet process

Sintered Nd-magnets are prepared by the raw materials being melted in a furnace, cast into a mold and cooled to form ingots. The ingots are pulverized and milled; the powder is then sintered into dense blocks. The blocks are then heat-treated, cut to shape, surface treated and magnetized.

In 2015, Nitto Denko Corporation of Japan announced their development of a new method of sintering neodymium magnet material. The method exploits an "organic/inorganic hybrid technology" to form a clay-like mixture that can be fashioned into various shapes for sintering. Most importantly, it is said to be possible to control a non-uniform orientation of the magnetic field in the sintered material to locally concentrate the field to, e.g., improve the performance of electric motors. Mass production is planned for 2017.^{[11][12]}

As of 2012, 50,000 tons of neodymium magnets are produced officially each year in China, and 80,000 tons in a "company-by-company" build-up done in 2013.^[13] China produces more than 95% of rare earth elements, and produces about 76% of the world's total rare-earth magnets.^[7]

Bonded Nd-magnets are prepared by melt spinning a thin ribbon of the NdFeB alloy. The ribbon contains randomly oriented Nd₂Fe₁₄B nano-scale grains. This ribbon is then pulverized into particles, mixed with a polymer, and either compression- or injection-molded into bonded magnets. Bonded magnets offer less flux intensity than sintered magnets, but can be net-shape formed into intricately shaped parts, as is typical with Halbach arrays or arcs, trapezoids and other shapes and assemblies (e.g. Pot Magnets, Separator Grids, etc.).^[14] There are approximately 5,500 tons of Neo bonded magnets produced each year. In addition, it is possible to hot-press the melt spun nanocrystalline particles into fully dense isotropic magnets, and then upset-forge or back-extrude these into high-energy anisotropic magnets.

Properties

Grades

Neodymium magnets are graded according to their maximum energy product, which relates to the magnetic flux output per unit volume. Higher values indicate stronger magnets and range from N35 up to N52. Letters following the grade indicate maximum operating temperatures (often the Curie temperature), which range from M (up to 100 °C) to EH (200 °C).^[15]

Grades of Neodymium magnets:^[16]

- N35-N52
- N33M-N48M
- N30H-N45H
- N30SH-N42SH
- N30UH-N35UH
- N28EH-N35EH

Magnetic properties

Some important properties used to compare permanent magnets are:

Remanence (B_r)

which measures the strength of the magnetic field

Coercivity (H_{ci})

the material's resistance to becoming demagnetized

Energy product (BH_{max})

the density of magnetic energy

Curie temperature (T_C)

the temperature at which the material loses its magnetism

Neodymium magnets have higher remanence, much higher coercivity and energy product, but often lower Curie temperature than other types. Special neodymium magnet alloys that include terbium and dysprosium have been developed that have higher Curie temperature, allowing them to tolerate higher temperatures.^[17] The table below compares the magnetic performance of neodymium magnets with other types of permanent magnets.

Magnet	B_r (T)	H_{ci} (kA/m)	BH_{max} (kJ/m ³)	T_C	
				(°C)	(°F)
Nd ₂ Fe ₁₄ B (sintered)	1.0–1.4	750–2000	200–440	310–400	590–752
Nd ₂ Fe ₁₄ B (bonded)	0.6–0.7	600–1200	60–100	310–400	590–752
SmCo ₅ (sintered)	0.8–1.1	600–2000	120–200	720	1328
Sm(Co, Fe, Cu, Zr) ₇ (sintered)	0.9–1.15	450–1300	150–240	800	1472
Alnico (sintered)	0.6–1.4	275	10–88	700–860	1292–1580
Sr-ferrite (sintered)	0.2–0.78	100–300	10–40	450	842




Neodymium magnets (small cylinders) lifting steel spheres. Such magnets can easily lift thousands of times their own weight.

Physical and mechanical properties

Ferrofluid can be used to disclose a powerful neodymium magnet's field

Comparison of physical properties of sintered neodymium and Sm-Co magnets^[18]

Property	Neodymium	Sm-Co
Remanence (T)	1–1.3	0.82–1.16
Coercivity (MA/m)	0.875–1.99	0.493–1.59
Relative permeability	1.05	1.05
Temperature coefficient of remanence (%/K)	−0.12	−0.03
Temperature coefficient of coercivity (%/K)	−0.55..−0.65	−0.15..−0.30
Curie temperature (°C)	320	800
Density (g/cm ³)	7.3–7.5	8.2–8.4
CTE, magnetizing direction (1/K)	5.2×10^{-6}	5.2×10^{-6}
CTE, normal to magnetizing direction (1/K)	-0.8×10^{-6}	11×10^{-6}
Flexural strength (N/mm ²)	250	150
Compressive strength (N/mm ²)	1100	800
Tensile strength (N/mm ²)	75	35
Vickers hardness (HV)	550–650	500–650
Electrical resistivity (Ω·cm)	$(110–170) \times 10^{-6}$	86×10^{-6}

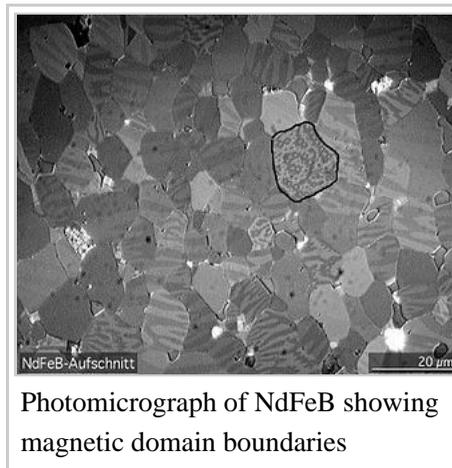

Photomicrograph of NdFeB showing magnetic domain boundaries

Corrosion problems

Sintered Nd₂Fe₁₄B tends to be vulnerable to corrosion, especially along grain boundaries of a sintered magnet. This type of corrosion can cause serious deterioration, including crumbling of a magnet into a powder of small magnetic particles, or spalling of a surface layer.

This vulnerability is addressed in many commercial products by adding a protective coating to prevent exposure to the atmosphere. Nickel plating or two-layered copper-nickel plating are the standard methods, although plating with other metals, or polymer and lacquer protective coatings are also in use.^[19]

Hazards

The greater forces exerted by rare-earth magnets create hazards that may not occur with other types of magnet. Neodymium magnets larger than a few cubic centimeters are strong enough to cause injuries to body parts pinched between two magnets, or a magnet and a ferrous metal surface, even causing broken bones.^[20]

Magnets that get too near each other can strike each other with enough force to chip and shatter the brittle



These neodymium magnets corroded severely after 5 months of weather exposure

material, and the flying chips can cause various injuries, especially eye injuries. There have even been cases where young children who have swallowed several magnets have had sections of the digestive tract pinched between two magnets, causing injury or death.^[21] The stronger magnetic fields can be hazardous to mechanical and electronic devices, as they can erase magnetic media such as floppy disks and credit cards, and magnetize watches and the shadow masks of CRT type monitors at a greater distance than other types of magnet.

Applications

Existing magnet applications

Neodymium magnets have replaced alnico and ferrite magnets in many of the myriad applications in modern technology where strong permanent magnets are required, because their greater strength allows the use of smaller, lighter magnets for a given application. Some examples are:

- Head actuators for computer hard disks
- Erase heads for cheap cassette recorders
- Magnetic resonance imaging (MRI)
- Mechanical e-cigarette firing switches
- Locks for doors
- Loudspeakers and headphones
- Magnetic bearings and couplings
- Benchtop NMR spectrometers
- Electric motors:
 - Cordless tools
 - Servomotors
 - Lifting and compressor motors
 - Synchronous motors
 - Spindle and stepper motors
 - Electrical power steering
 - Drive motors for hybrid and electric vehicles. The electric motors of each Toyota Prius require 1 kilogram (2.2 pounds) of neodymium.^[17]
 - Actuators
- Electric generators for wind turbines (only those with permanent magnet excitation)
 - direct-drive wind turbines require c. 600 kg of PM material per megawatt
 - turbines using gears require less PM material per megawatt
- Toys^[22]



Ring magnets



Most hard disk drives incorporate strong magnets



This manually-powered flashlight uses a neodymium magnet to generate electricity

Neodymium content is estimated to be 31% of magnet weight^[7]

New applications

In addition, the greater strength of neodymium magnets has inspired new applications in areas where magnets

were not used before, such as magnetic jewelry clasps, children's magnetic building sets (and other neodymium magnet toys) and as part of the closing mechanism of modern sport parachute equipment.^[23] They also are the main metal in the formerly popular desk-toy magnets, "Buckyballs", though some US retailers have chosen not to sell them due to child-safety concerns.^[24]

The strength and magnetic field homogeneity on neodymium magnets has also opened new applications in the medical field with the introduction of open magnetic resonance imaging (MRI) scanners used to image the body in radiology departments as an alternative to superconducting magnets that use a coil of superconducting wire to produce the magnetic field.

Neodymium magnets are used as a surgically placed anti-reflux system which is a band of magnets^[25] surgically implanted around the lower esophageal sphincter to treat gastroesophageal reflux disease (GERD).^[26]

See also

- Lanthanide metals
- Neodymium magnet toys
- Rare-earth magnet
- Samarium-cobalt magnet
- Transition metal substitutions like NdCoB

References

1. "What is a Strong Magnet?". *The Magnetic Matters Blog*. Adams Magnetic Products. October 5, 2012. Retrieved October 12, 2012.
2. Fraden, Jacob (2010). *Handbook of Modern Sensors: Physics, Designs, and Applications, 4th Ed.* USA: Springer. p. 73. ISBN 1441964657.
3. "What are neodymium magnets?". *wiseGEEK website*. Conjecture Corp. 2011. Retrieved October 12, 2012.
4. Chikazumi, Soshin (2009). *Physics of Ferromagnetism, 2nd Ed.* OUP Oxford. p. 187. ISBN 0191569852.
5. "Magnetic Anisotropy". Hitchhiker's Guide to Magnetism. Retrieved 2 March 2014.
6. Template:Cite boo
7. Chu, Steven. Critical Materials Strategy (http://energy.gov/sites/prod/files/DOE_CMS2011_FINAL_Full.pdf) *United States Department of Energy*, December 2011. Accessed: 23 December 2011.
8. Peter Robison & Gopal Ratnam (29 September 2010). "Pentagon Loses Control of Bombs to China Metal Monopoly". Bloomberg News. Retrieved 24 March 2014.
9. "Research Funding for Rare Earth Free Permanent Magnets". ARPA-E. Retrieved 23 April 2013.
10. "Manufacturing Process of Sintered Neodymium Magnets". American Applied Materials Corporation.
11. "World's First Magnetic Field Orientation Controlling Neodymium Magnet". Nitto Denko Corporation. 24 August 2015. Retrieved 28 September 2015.
12. "Potent magnet that can be molded like clay developed". Asahi Shimbun. 28 August 2015. Retrieved 28 September 2015.
13. "The Permanent Magnet Market – 2015" (PDF). *Magnetics 2013 Conference*. Magnetics 2013 Conference. February 7, 2013. Retrieved November 28, 2013.
14. "An Introduction to Neodymium Magnets". *NdFeB-Info website*. e-Magnets UK. Retrieved November 28, 2013.
15. "Magnet Grade Chart". *Magnet Grade Chart*. Amazing Magnets, LLC. Retrieved December 4, 2013.



Neodymium magnet spheres assembled in the shape of a cube

16. "Grades of Neodymium magnets" (PDF) (<http://www.china-magnet.net/neodymium-magnet/Grade%20of%20neodymium%20magnet.pdf>). Everbeen Magnet. Retrieved December 6, 2015.
17. As hybrid cars gobble rare metals, shortage looms (<http://www.reuters.com/article/newsOne/idUSTRE57U02B20090831>), Reuters, August 31, 2009.
18. Juha Pyrhönen; Tapani Jokinen; Valéria Hrabovcová (2009). *Design of Rotating Electrical Machines*. John Wiley and Sons. p. 232. ISBN 0-470-69516-1.
19. Drak, M.; Dobrzanski, L.A. (2007). "Corrosion of Nd-Fe-B permanent magnets" (PDF). *Journal of Achievements in Materials and Manufacturing Engineering*. **20** (1–2).
20. Swain, Frank (March 6, 2009). "How to remove a finger with two super magnets". *The Sciencepunk Blog*. Seed Media Group LLC. Retrieved 2009-06-28.
21. "CPSC Safety Alert: Ingested Magnets Can Cause Serious Intestinal Injuries" (PDF). U.S. Consumer Product Safety Commission. Retrieved 13 December 2012.
22. Constantinides, Steve (2011). "Rare Earth Materials Update – May, 2011". *SMMA Motor and Motion Association conference 2011*. Arnold Magnetic. Retrieved February 11, 2013.
23. "Options Guide" (http://www.unitedparachutetechnologies.com/index.php?option=com_content&task=view&id=22). United Parachute Technologies. Archived (https://web.archive.org/web/20110717163453/http://www.unitedparachutetechnologies.com/index.php?option=com_content&task=view&id=22) July 17, 2011, at the Wayback Machine.
24. O'Donnell, Jayne (July 26, 2012). "Feds file suit against Buckyballs, retailers ban product" (<http://usatoday30.usatoday.com/money/industries/retail/story/2012-07-25/buckyballs-ban/56481316/1>). *USA Today*.
25. "TAVAC Safety and Effectiveness Analysis: LINX® Reflux Management System".
26. "The linx reflux management system: stop reflux at its source". Torax Medical Inc.

Further reading

- MMPA 0100-00, Standard Specifications for Permanent Magnet Materials (<https://web.archive.org/web/20140722210259/http://www.intl-magnetics.org/pdfs/0100-00.pdf>)
- K.H.J. Buschow (1998) *Permanent-Magnet Materials and their Applications*, Trans Tech Publications Ltd., Switzerland, ISBN 0-87849-796-X
- Campbell, Peter (1994). *Permanent Magnet Materials and their Application*. New York: Cambridge University Press. ISBN 0-521-24996-1.
- Furlani, Edward P. (2001). *Permanent Magnet and Electromechanical Devices: Materials, Analysis and Applications*. London: Academic Press. ISBN 0-12-269951-3.
- Brown, D; Ma, Bao-Min; Chen, Zhongmin (2002). "Developments in the processing and properties of NdFeB-type permanent magnets". *Journal of Magnetism and Magnetic Materials*. **248** (3): 432–440. Bibcode:2002JMMM..248.432B. doi:10.1016/S0304-8853(02)00334-7.
- The Dependence of Magnetic Properties and Hot Workability of Rare Earth-Iron-Boride Magnets Upon Composition (https://web.archive.org/web/20120425082651/http://www.magnequench.com/assets/content/magnequench/mag_ref/mag_pps/pps_040701/IEEE2004_vMAG40.pdf).

External links

- Magnet Man (<http://www.coolmagnetman.com/magindex.htm>) Cool experiments with magnets
- Geeky Rare-Earth Magnets Repel Sharks, Genevieve Rajewski, 05.15.07 , wired.com (<https://web.archive.org/web/20140318172638/http://www.wired.com/gadgets/miscellaneous/news/2007/05/sharkmagnets>)
- Concern as China clamps down on rare earth exports, Cahal Milmo, 01.02.10, independent.co.uk (<http://www.independent.co.uk/news/world/asia/concern-as-china-clamps-down-on-rare-earth-exports-1855387.html>)

- Bowley, Roger. "More with Magnets". *Sixty Symbols*. Brady Haran for the University of Nottingham.

Retrieved from "https://en.wikipedia.org/w/index.php?title=Neodymium_magnet&oldid=757841207"

Categories: [Magnetic alloys](#) | [Types of magnets](#) | [Ferromagnetic materials](#) | [Loudspeaker technology](#)

- This page was last modified on 2 January 2017, at 01:31.
- Text is available under the Creative Commons Attribution-ShareAlike License; additional terms may apply. By using this site, you agree to the Terms of Use and Privacy Policy. Wikipedia® is a registered trademark of the Wikimedia Foundation, Inc., a non-profit organization.